



Experiment on micron-sized particle production of iron ore by rapid unloading of liquid CO₂

Fan YongBo *, Duan WenJie, Li ShiHai, Qiao JiYan

Key Laboratory for Mechanics in Fluid Solid Coupling Systems, Institute of Mechanics, Chinese Academy of Sciences

ARTICLE INFO

Article history:

Received 8 June 2017

Received in revised form 18 October 2017

Accepted 7 December 2017

Available online 16 December 2017

Keywords:

Liquid CO₂

Rapid unloading

Iron ore

Micron-sized particles

ABSTRACT

The average iron content of iron ore is <30%; therefore, crushing, grinding, milling and other processing techniques must be executed before smelting. Currently, it is expensive to break iron ores using mechanical grinding. Experiments have been carried out to develop a novel approach of producing iron ore powder. First, the iron ore is placed in a high-pressure chamber, and then liquid CO₂ is injected into the chamber. Second, considering energy recycling, after the iron ore pores are filled with liquid CO₂, dissociative liquid CO₂ is substituted and collected for cyclic utilization. Third, an initial high pressure is applied inside the chamber using a water pump in order to increase the energy input. Fourth, the pressure is rapidly unloaded. After penetration and gasification expansion, the iron ore will immediately be converted into micron-sized particles. Laser grain size analysis indicated that the grain size of the iron ore particles ranges between 30 and 50 μm, which will satisfy the requirements of gravity separation, magnetic separation and the flotation process. This is a highly efficient and low-cost method that has excellent industrial promotion value.

© 2017 Elsevier B.V. All rights reserved.

1. Introduction

Iron powder is in great demand, especially for the auto industry, manufacturing, and the production of permanent magnets [1]. The production of special steel and alloys from iron powder is also of great interest. In this context, research is underway to expand the range and improve the quality of iron powder and also to find additional sources of raw materials for powder production. Conventional techniques used in the production of iron ore particles are based on mechanical methods, including crushing, grinding and milling processes. Mechanical crushing [2] is represented as periodic processes that accumulate energy in zones of residual stress and discharge them during fracturing. The cost of crushing accounts for a large proportion of the iron powder production costs.

Besides being a greenhouse gas and a major component of the carbon cycle in nature, carbon dioxide (CO₂) is a substance of major industrial importance [3]. Numerous industrial processes use CO₂, but the total amount of CO₂ used in industry is equivalent to about 2% of the CO₂ emitted globally by power plants into the atmosphere; it is non-toxic, non-corrosive and non-abrasive. Furthermore CO₂ is non-conducting and chemically inert. It is used for cryogenic cooling; separation technologies; chemical extractions; polymerization; powder processing; spray painting and coating; and various chemical reactions, among other processes. Liquid CO₂ blasting is a physical blasting method developed in the early 1960s in the United States and other

developed countries, and the first cardox blaster was successfully developed by the US Aiduokesi Company [4–6]. The technology is based on the rapid and large volume expansion characteristics when liquid CO₂ is converted into a gas, and rock breaking could occur because of the stress wave generated by the high-pressure gas. Other countries such as England, France, Russia, Poland and Norway have also developed this method. The blasting of liquid CO₂ is non-explosive, and it accounted for 20% of total coal mining production in the United States in the early 1960s.

It is worth mentioning that CO₂ is the most widely used supercritical fluid because it has a relatively low critical value and a moderate critical pressure ($T_c = 31.0\text{ }^\circ\text{C}$, $P_c = 7.38\text{ MPa}$). It has unique features such as liquid-like density and gas-like diffusivity, which are important for the production of micron-sized particles of iron ore. Several methods have been broadly reviewed and implemented [7–10], including the rapid expansion of supercritical solutions (RESS), solution enhanced dispersion by supercritical fluid (SEDS), supercritical solvent impregnation (SSI), supercritical fluid extraction of emulsions (SFEE), gas antisolvent crystallization (GAS), supercritical antisolvent precipitation (SAS), precipitation by compressed antisolvent (PCA), an aerosol solvent extraction system (ASES) and particle from gas-saturated solutions (PGSS).

Liquid CO₂ blasting is considered physical blasting. The core concept underlying this technology is the blasting system, which consists of a high-pressure chamber containing an inlet control valve, seal cover and sealing ring, heating apparatus, rupture disk, and release holes following the order from top to bottom. A high-pressure chamber filled with liquid CO₂ is placed in the borehole, and the heater apparatus heats

* Corresponding author.
E-mail address: ybfan@imech.ac.cn (F. YongBo).

the liquid CO₂. The pressure in the high-pressure chamber increases rapidly, and as soon as the pressure of liquid CO₂ in the high-pressure chamber exceeds the shearing strength of the rupture disk, the rupture disk is damaged and high pressure liquid CO₂ will be released at high speed and will crush the nearby rock. This process brings about the phase change of liquid CO₂ and then causes a dramatic expansion in the volume of liquid CO₂. No sparks appear during the blasting process or the transport process, and both the storage and use of the materials are convenient. By utilizing the phase change energy of CO₂ to break the rock mass, instantaneous high temperature is necessary. Compared with general blasting, the blasting of liquid CO₂ has the characteristics of slow expansion and steady shearing, and it is suitable for brittle rock. The blasting pressure of liquid CO₂ is lower than that of explosives, about one-third that of black powder and one-sixth that of ammonium nitrate explosives [11]. Black powder consists of KNO₃, S, and C.

Conventional techniques used for the production of micron-sized particles of iron ore are mostly based on mechanical methods such as crushing, grinding, milling and other processes. Powder characteristics are mainly determined by the average grain size, size distribution and particle shape [12–14], and new types of iron powders with special and improved properties have been developed and have conquered the market. At present, there are generally two production methods that together account for >90% of the global production of iron powders, viz. the Hoganas sponge iron process and the water-atomizing process. The industrial production of iron powder started in 1937 based on the incentive of the General Motors Corporation in the USA [15,16].

Aluminum was not “discovered” until 1808 (about 200 years ago), although early civilizations used aluminum-bearing clays to make pottery, and aluminum salts were used to make dyes and medicines [17]. Almost all commercial aluminum and aluminum alloy powders or granulates that are used in powder metallurgy (PM) production are made through the dispersion of the molten phase by atomization [18], centrifuging or granulation [19]. Other ultrafine powders are produced by high-pressure gas atomization or ultrasonic gas atomization. For example, the Hartman Shock Wave Tube [20] that generates shock waves with ultrasonic frequencies and supersonic gas velocity to produce the finest powder with a median grain size in the range 10–20 μm is well established.

Interest in synthesizing copper powder has increased considerably during the past few years because of its high electrical conductivity, relatively higher melting point, low electrochemical migration behavior and low material cost [21,22]. Granular copper powder can be produced by a number of methods, e.g., atomization, oxide reduction, electrolysis and hydrometallurgy [23]. Of the above methods, atomization and oxide reduction are presently applied on a large global scale. Each method yields a powder with certain inherent characteristics.

Cement is a fine powder that is the principal strength-giving and property-controlling component of concrete [24]. Cement is made by crushing and grinding calcium carbonate (limestone), silica (sand), alumina and iron ore in appropriate proportions and heating the resulting mixture in a kiln to approximately 1500 °C. Common materials used to manufacture cement include limestone, shells, and chalk or marl combined with shale, clay, slate, blast furnace slag, silica sand, and iron ore. These ingredients, when heated at high temperatures, form a rock-like substance that is ground into the fine powder that we commonly think of as cement.

The production of iron powders, aluminum alloy powders, copper powders and cement utilizes mechanical and chemical methods such as crushing, grinding, milling and heating. The first observation related to the possibility of obtaining ultrafine powders through supercritical fluid (SF) processing was made in 1876 [25]. The production of particles by rapid expansion of liquid CO₂ was first noted over thirty years ago [26]. The application of liquid CO₂ as an alternative to these conventional crushing processes has been an active field of research and innovation. The main motivation for this is the possibility of exploiting the peculiar properties of liquid CO₂, such as its gas-like diffusivity,

liquid-like density and low-viscosity [10], which are especially significant for micron-sized particle production processes. Moreover, these properties can easily be obtained with changes in pressure and temperature [27].

In this paper, we developed a new alternative method for the production of micron-sized particles of iron ore by rapid unloading of liquid CO₂; the grain size of the iron ore particle is between 30 and 50 μm, and 90% of the grains are smaller than 98.5 μm.

2. Introduction of rapid unloading of liquid CO₂ used in the production of micron-sized iron ore particles

The rapid unloading of liquid CO₂ is as follows: the whole process is carried out in a high-pressure chamber, which consists of a rupture disk, seal cover and sealing ring, inlet control valve and needle valve. The rupture disk is located at the end of the high-pressure chamber. The seal cover and sealing ring not only avoid liquid CO₂ leakage but also ensure the installation of the rupture disk.

Currently, the overall process includes CO₂ liquefaction, CO₂ filling, CO₂ substitution, high pressure initialization, unloading and CO₂ gasification.

First, iron ores are placed in the high-pressure chamber, and after sealing, liquid CO₂ is injected. The injection temperature and pressure are controlled at –10 °C and 3 MPa, respectively, in order to ensure that the injected CO₂ is liquid and energy consumption is minimal. As indicated in a previous study of CO₂ liquefaction characteristics [28], the total power of the liquefaction device, which is combined with the compression and refrigeration components, is smallest at a 3-MPa compression pressure, and the transition temperature of CO₂ at that pressure is approximately –10 °C. The most economical process of CO₂ liquefaction is to first compress the CO₂ gas until a 3-MPa pressure is reached and then to cool the gas to cause the CO₂ to condense. If the liquid CO₂ is produced at the same site as particle production, the most economical option is to keep the liquid CO₂ at the T and P under which it was produced. In this way, the economically optimal CO₂ injection process occurs at –10 °C and 3 MPa.

After approximately 20–30 s, the saturated penetration time of the liquid CO₂ under 3 MPa is reached. Second, dissociative liquid CO₂ between the iron ore will be substituted by water and collected for cyclic utilization. It is emphasized that the water pressure is slightly higher than 3 MPa. Third, higher pressure is applied to the water inside the chamber through the water pump in order to increase the energy input. Fourth, the liquid CO₂ is rapidly unloaded.

The liquefaction process of CO₂ includes controlling the pressure and temperature; based on the physical characteristics of CO₂, when temperature and pressure are controlled at –10 °C and 3 MPa, respectively, economic benefits are maximized. The density of CO₂ under different pressures and temperatures is illustrated in Table 1.

For the purpose of recycling the liquid CO₂, several procedures relating to CO₂ substitution should be carried out. Dissociative liquid CO₂ can be replaced by water, and liquid CO₂ inside the iron ore does not spread out during the CO₂ substitution process. Based on the porosity of the iron ore, about 95% of the dissociative liquid CO₂ can be substituted. The CO₂ substitution apparatus is illustrated in Fig. 1.

First, the outlet of the high-pressure chamber is equipped with a needle valve to control the amount of CO₂ substitution and the sealing process.

Second, the initial filling pressure of the liquid CO₂ in the high-pressure chamber is approximately 3 MPa; the saturated penetration time of the iron ore is approximately 20 s, illustrated in Fig. 2. We performed a penetration test of the iron ore. After the iron ore is placed in the sealed container, the high pressure liquid CO₂ is injected at one end of the sealed container, illustrated in Fig. 3. The discharge of liquid CO₂ is observed at the other end of the sealed container, illustrated in Fig. 4. When the discharge of liquid CO₂ becomes stable, it is believed that the iron ore reaches infiltration saturation. According to the

Table 1
Density of CO₂ under different pressure and temperature.

T(°C) \ P (Mpa)	0.1	1	2	3	4	5	6	7	8	9	10
-10	2.03	21.9	48.8	98.5	99.1	99.6	100.2	100.7	101.2	101.6	102.1
0	1.95	20.8	45.6	77.3	93.2	94.1	94.8	95.5	96.2	96.8	97.4
10	1.88	19.9	43	71	108	869	882	893	903	912	920
20	1.82	19.1	40.8	66.2	97.5	141	783	809	828	843	856
30	1.75	18.4	38.8	62.2	89.8	124	171	267	702	744	772

G L

equation $K = 2000 \frac{P_{atm} \mu Q_a L}{A(P_1 - P_2)} (P_{atm} - \text{atmospheric pressure}; \mu - \text{viscosity}; Q_a - \text{velocity}; L - \text{length of iron ore}; A - \text{cross-sectional area}; P_1 - \text{import pressure}; P_2 - \text{outlet pressure})$, the permeability of the iron ore at 15 MPa is $1 \times 10^{-6} \mu\text{m}^2$.

Third, after saturated penetration, the water pump starts to run. When the water pressure is slightly higher than 3 MPa, we need to open the inlet control valve and the needle valve of the high pressure chamber simultaneously to substitute liquid CO₂; when water flows slowly from the needle valve, the inlet control valve and needle valve should be closed. The whole process of liquid CO₂ substitution is accomplished. The results confirm that the grain size of the iron ore particles after liquid CO₂ substitution is slightly larger than that resulting from direct powder production but is similar to that resulting from the conventional crushing methods.

The total energy input is related to the grain size of the iron ore powder. The higher the energy input, the greater the pressure of the liquid CO₂ stored in the iron ore. A higher pressure gradient is generated when gasification occurs, and a finer iron ore powder is obtained. In order to increase the input energy, water pressure is applied through the inlet control valve by the water pump after CO₂ substitution; the high water pressure apparatus is illustrated in Fig. 5. Because the compression coefficient of water is small, a high initial water pressure (50 MPa, 80 MPa) is easily reached.

When the pressure increases, the rupture disks will burst. The time of rupture disk bursting is approximately 5–8 ms, and the high pressure is reduced to zero during this time. During the unloading process of the liquid CO₂, the gasification boundary of liquid CO₂ is in a certain position within the iron ore where the gasification pressure is maintained at 3 MPa, and the iron ore body between the outer surface and gasification boundary is then converted into micron-sized iron ore particles. Subsequently, the gasification boundary gradually moves inwards, and finally, the iron ore body is turned into powder layer by layer. Under the high pressure gradient, micron-sized iron ore particles are obtained.

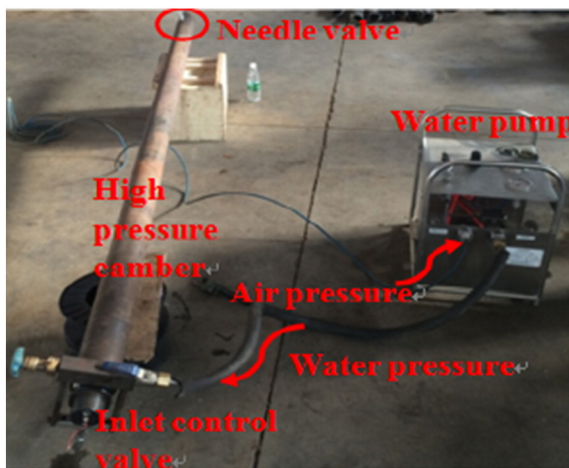


Fig. 1. CO₂ substituting apparatus.

3. Implementation

3.1. Model test for micron-sized particles of iron ore

In addition to the above procedures (CO₂ liquefaction, CO₂ filling, CO₂ substitution, high pressure initialization, unloading and CO₂ gasification), the model test includes the collection of iron ore powders. Different types of model tests have been carried out, including direct powder production, powder production after CO₂ substitution, and powder production after CO₂ substitution and high pressure initialization.

The iron ore is weighed before being placed in the high-pressure chamber. The equivalent diameter of the iron ore is <60 mm because the inner diameter of the high pressure chamber is 63 mm. The inner volume of the high pressure chamber is approximately 0.01 m³, and according to the volume ratio of densely packed particles of equal diameter, the porosity is approximately 35–40%; therefore, the mass of the iron ore is about 7 kg. After sealing, CO₂ filling, liquid CO₂ substitution and high water pressure initialization, the high pressure chamber is placed in the collection container to effectively collect the iron ore powder; the apparatus is illustrated in Fig. 6. Eventually, the rupture disks burst, and the iron ore powder sprays into the collection container.

3.2. Grain size and grain size distribution measurements

Grain size is a key factor that determines the performance of different organic and inorganic materials. Data analysis indicates that both the average grain size and the grain size distribution (GSD) are related to the initial water pressure and the liquid CO₂ substitution. The direct powder production result is illustrated in Fig. 7. The grain size of the iron ore particles ranges from 30 μm to 50 μm, and grain sizes <98.5 μm account for 90% of the grains, as illustrated in Fig. 8. The comparison between the iron ore powder under the condition of direct powder production and powder production after CO₂ substitution is illustrated in Table 2. The grain size of the iron ore after liquid CO₂ substitution includes more coarse powders of iron ore and a few fine powders. From the experiment of direct powder production, the percent grain size <43 μm accounts for 40%, which makes it too fine for the gravity separation, magnetic separation and flotation processes. Based on the experiment of powder production after CO₂ substitution, the percent grain size <147 μm accounts for 60%, which is suitable for gravity separation, magnetic separation and flotation processes. In summary, the micron-sized particles of iron ore produced by powder

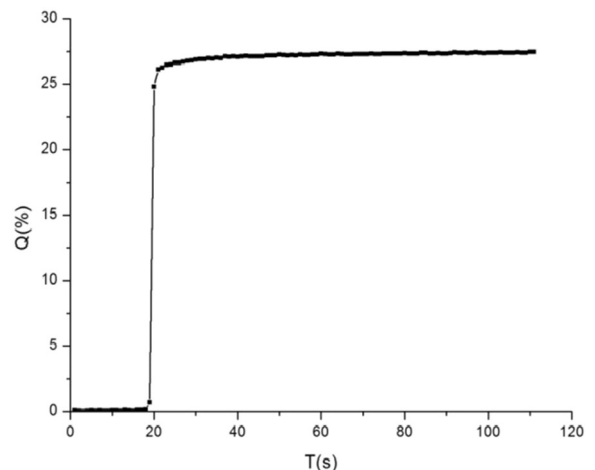


Fig. 2. Saturated penetration time of iron ore.

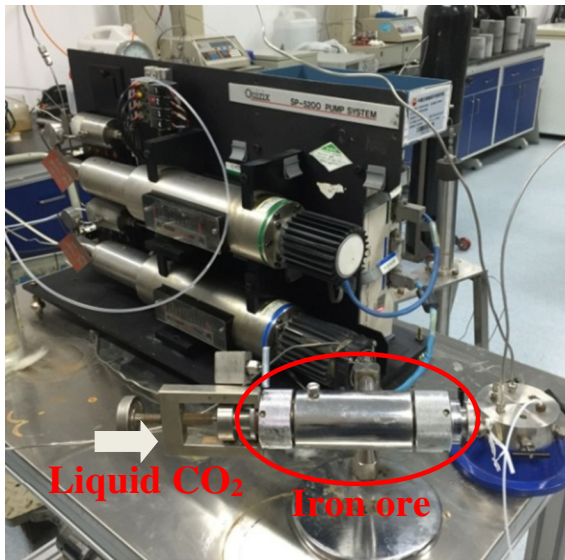


Fig. 3. Penetration test of the iron ore.

production after CO₂ substitution are ideal because of the optimized grain size distribution and low cost.

The grain size distribution of the iron ore powder under different initial water pressure is illustrated in Fig. 9. The initial water pressures are 50 MPa (explosive 300 g), 50 MPa (explosive 400 g), 80 MPa (explosive 200 g), and 80 MPa (explosive 440 g). Fewer particles larger than 297 μm and more particles smaller than 147 μm will be obtained under high initial water pressure. It is well accepted that a grain size smaller than 147 μm accounts for the main component when the initial water pressure reaches 80 MPa. The initial water pressure provides high energy to the liquid CO₂ stored in the iron ore; therefore, when the rupture disk is broken, there is a large volume expansion, and more small-sized iron ore powders will be obtained. Based on Fig. 9, the percent grain size <147 μm accounts for 80% when the initial water pressure is 80 MPa, compared with 50% when the initial water pressure is 50 MPa. The effect of the initial water pressure is greater than the amount of the explosive in the powder production of the iron ore, and based on the above conclusion, the explosive can gradually be replaced by a high initial water pressure.

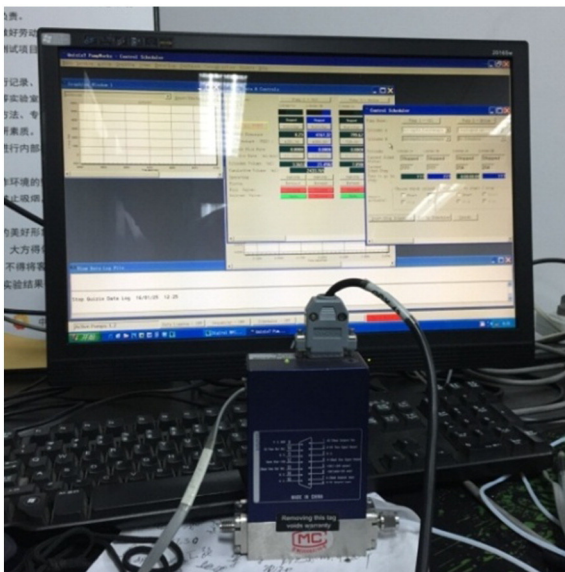


Fig. 4. Discharge of liquid CO₂ monitoring.



Fig. 5. High pressure initialization apparatus.

4. Reliability and reusability

In order to verify the reliability and the reusability of the powdering method, a series of experiments on iron ore powdering were carried out, including hematite, refractory iron ore, low-grade iron ore, and magnetite powdering, as illustrated in Fig. 10. In addition to iron ore powdering by unloading of liquid CO₂, bauxite and limestone powdering experiments were also carried out, and the particles obtained are illustrated in Fig. 11. The grain size of the bauxite and limestone particles ranged from 4 μm to 6 μm and from 10 μm to 20 μm , respectively, as illustrated in Fig. 12. The results confirmed that obtaining

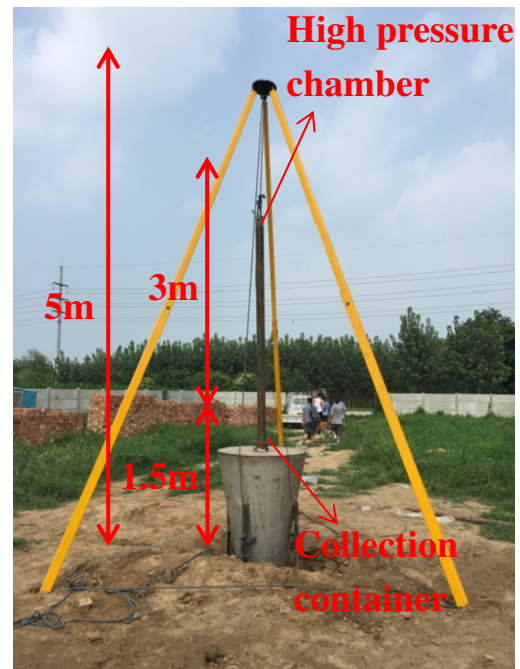


Fig. 6. Platform for iron ore powder production.

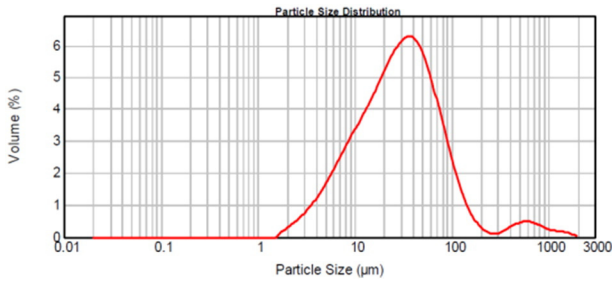


Fig. 7. Grain size distribution of iron ore particles.

micron-sized powder by rapid unloading of liquid CO₂ is feasible. In addition, the powdering method is green and energy efficient.

5. Analysis of economical benchmarking

The current cost of iron ore powder produced by ball milling in China is approximately 5.7 US dollars per ton of iron ore. The estimated cost of the rapid unloading procedure is approximately 1.0 US dollars per ton. The cost of the rapid unloading procedure has two components: power consumption and wear.

Power consumption is a linear function of liquid CO₂ usage. The power consumed during liquid CO₂ production is approximately 175 KWh per ton. The amount of liquid CO₂ used to produce iron ore powder varies based on the scale of the production. If the container scale has a radius of 1 m and a height of 10 m and 95% of the dissociative liquid CO₂ can be recycled, then the average usage of liquid CO₂ is 15 kg per ton of iron ore. Another source of power consumption is the pumping system. The average pumping cost for one ton of iron ore is approximately 0.7 KWh. The total power consumption for the processing of one ton of iron ore is 175 KWh/ton * 0.015 ton + 0.7 kWh = 3.3 KWh. The power price in China is 0.15 US dollars per KWh for industry usage. The power consumption is estimated as 0.5 US dollars per ton.

The wear cost is also affected by the scale of the production. Because the rapid unloading procedure does not have a liner cost in the current production procedure, the main wear cost is the rupture of disks. By using a variable-diameter outlet design, the size and thickness of the rupture disks could be reduced. The estimated wear cost is 0.52 US dollars per ton of iron ore.

6. Discussion

Rapid unloading of liquid CO₂, as demonstrated, can produce micron-sized particles of iron ore. This process is different from

Table 2
Grain composition of the iron ore particles.

Diameter of the powder (µm)	Direct powder production (explosive 440 g)	Powder production after CO ₂ substituting (explosive 440 g)
+ 50 (297)	14.99	40.57
+ 100 (147)	7.47	14.57
+ 150 (104)	9.43	11.61
+ 200 (74)	14.66	13.31
+ 260 (51)	10.24	7.02
+ 325 (43)	4.99	2.36
- 325 (<43)	38.22	10.56
Total	100.00	100.00

conventional methods, and the grain size distribution can be regulated by the controllable methods of the initial water pressure and CO₂ substitution. From the two briefly illustrated cases, the production of micron-sized particles of iron ore can evidently be employed advantageously. It should be pointed out that the method is an effective way to improve efficiency and save energy.

Based on the comparison of direct powder production and powder production after CO₂ substitution, there is now a general consensus that the grain size of iron ore powder after CO₂ substitution is larger than that resulting from direct powder production. In this case, further studies are needed to determine the extent of CO₂ substitution, which is the basis for the optimization of iron ore powder grading. However, what has not been delineated is the phase change of CO₂ at the time the rupture disk opens. It is well accepted that a pressure of 3 MPa is the gas-liquid conversion limit point, but whether the gas-liquid conversion interface of iron ore is the dominant factor needs to be determined, in other words, how does the gas-liquid conversion interface affect iron ore powdering? Among the questions that remain to be resolved is the process of iron ore powdering. Because the whole powdering process occurs inside a high-pressure chamber, only a pressure-time history curve can be obtained. To further determine the mechanism of iron ore powdering, X-rays or a transparent chamber deployed with a high-speed camera need to be adopted. The current iron ore powdering production experiments are under the combined effect of explosives and liquid CO₂. The experiments have indicated that the effect of explosives on powdering is not significant. Therefore, we can gradually increase the initial water pressure and reduce the use of explosives until no explosives are used. Optimization of the powdering process is likely to reduce the cost of iron ore powder production.

7. Conclusions

The results of the laboratory-scale experiments indicate that it is possible to produce micron-sized particles of iron ore using controllable methods of CO₂ substitution and initial water pressure.

The production of iron ore particles by rapid unloading of liquid CO₂ is a truly original approach, which is based on the physical characteristics of liquid CO₂, such as low viscosity, high permeability, and a high dilation coefficient. This approach is different from the traditional mechanical methods that use crushing, grinding and milling. Iron ore powder production after CO₂ substitution is an effective method, which not only optimizes the grain size distribution but also saves 95% of the liquid CO₂. The initial water pressure provides high energy to the liquid CO₂ stored inside the iron ore. The higher the initial water pressure, the higher the number of fine particles obtained. The effect of the initial water pressure is greater than that of the explosives in the powder production of the iron ore, and breaking through the rupture disk is the main effect of the explosives. Based on the above conclusion, the explosives can gradually be replaced by the initial water pressure.

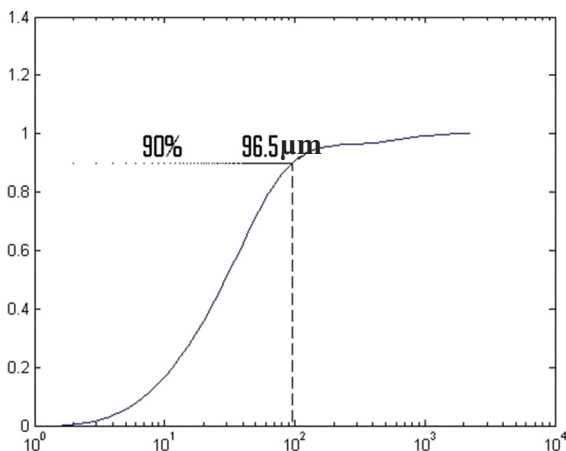


Fig. 8. Cumulative distribution of iron ore particles.

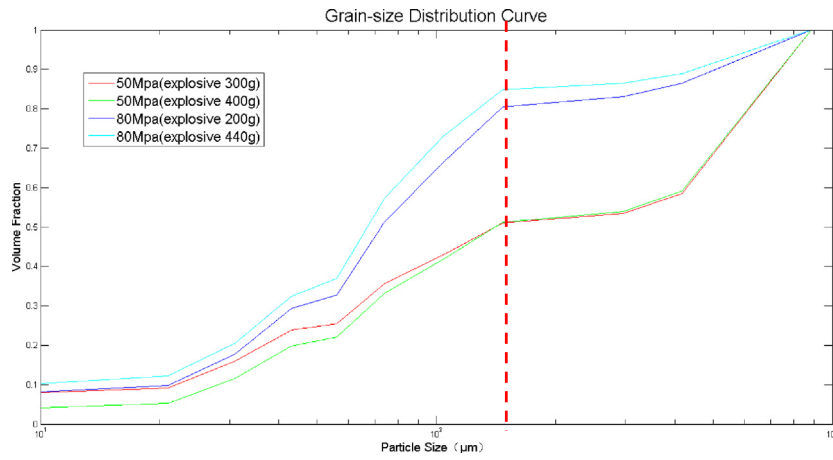


Fig. 9. grain size distribution curve of iron ore particles.

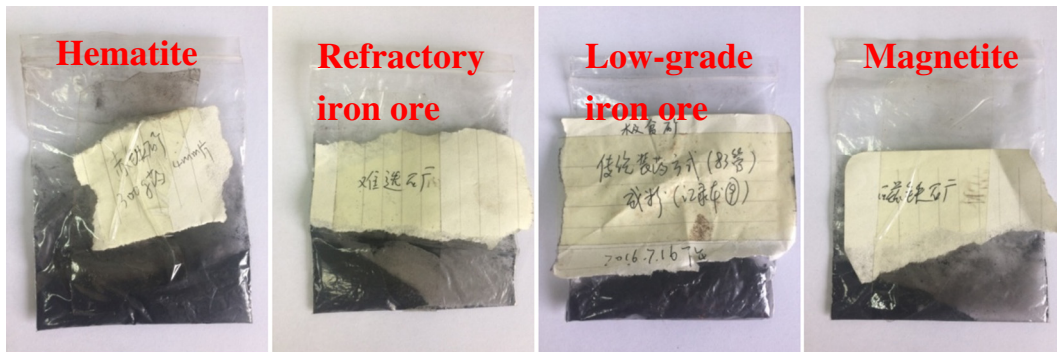


Fig. 10. Different types of iron ore powder.

Acknowledgments

The authors would like to sincerely thank Guo WX and Liu HQ for their help with the laboratory equipment. The work presented in this

paper was supported by the National Natural Science Foundation of China (11302229), the 973 Program (2015CB250903), and the Chinese Academy of Sciences Special Fund for Strategic Pilot Technology (XDB10030303). The authors are grateful for the support.



Fig. 11. Bauxite and limestone particles.

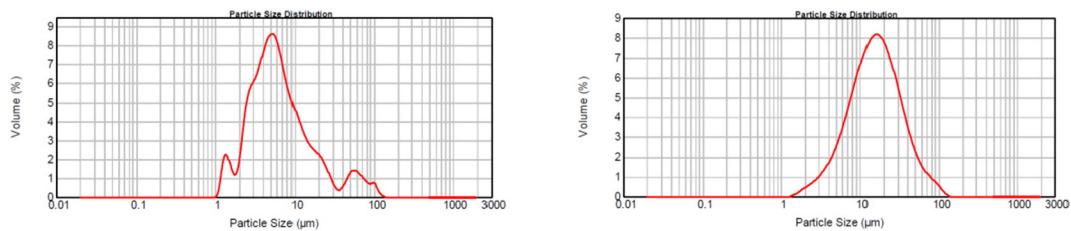


Fig. 12. Grain size distribution of bauxite and limestone particles.

References

- [1] I.M. Zelenova, Iron-ore concentrates in iron-powder production, *Steel in Translation* 39 (9) (2009) 827–830.
- [2] V.I. Molchanov, O.G. Selezneva, *Technical Methods of Activating Minerals by Crushing, Mechanization and Automation of Mining Operations*, 6, 1980 587–598.
- [3] Brahim Dincer, Calin Zamfirescu, *Sustainable Energy Systems and Applications [M]*, 2011 (1–816).
- [4] Z.X. Guo, Liquid cardox blaster and blasting on site [J], *Blasting* (1994) 72–74.
- [5] Y. Xu, Y.S. Cheng, Study on high-pressure gas blasting mechanism and model experiment [J], *Coal Mine Blasting* 34 (3) (1996) 1–15.
- [6] P. Shao, Y. Xu, Y.S. Cheng, Research on the test system of air shooting [J], *Explosive Materials* 26 (5) (1997) 6–8.
- [7] P. Alessi, A. Cortesi, I. Kikic, F. Carli, Rapid expansion of supercritical solutions technology: production of fine particles of steroid drugs, *Supercritical Fluid Methods and Protocols* (2000) 201–208.
- [8] J. Fages, H. Lochard, J.J. Letourneau, M. Sauceau, E. Rodier, Particle generation for pharmaceutical applications using supercritical fluid technology, *Powder Technol.* 141 (3) (2004) 219–226.
- [9] J.C. Maria, M. Angel, M. Facundo, V. Salima, Encapsulation and co-precipitation processes with supercritical fluids: fundamentals and applications, *J. Supercrit. Fluids* 47 (2009) 546–555.
- [10] H. Norazlina, Y. Kamal, Supercritical carbon dioxide-assisted process in synthesis of polymer/clay melt [J], *Macromol. Res.* 23 (5) (2015) 403–417.
- [11] Y. Xu, Y.S. Cheng, J.L. Wang, High-pressure gas blasting [J], *J. Coat. Sci. Technol.* 25 (5) (1997) 52–53.
- [12] B. Masoud, R. Sima, Production of micro- and nano-composite particles by supercritical carbon dioxide [J], *J. Supercrit. Fluids* 40 (2007) 263–283.
- [13] X. Fu, D. Huck, L. Makein, B. Armstrong, U. Willen, T. Freeman, Effect of particle shape and size on flow properties of lactose powders, *Particuology* 10 (2) (2012) 203–208.
- [14] M. Ghambari, M.E. Shaibani, N. Eshraghi, Production of grey cast iron powder via target jet milling, *Powder Technol.* 221 (2012) 318–324.
- [15] R.M. German, *Powder Metallurgy of Iron and Steel*, John Wiley & Sons, Inc, 605 Third Ave, New York, NY 10016, USA, 1998 496.
- [16] F. Thummler, R. Oberacker, *Introduction to Powder Metallurgy*, Oxford Science Publications, 1993 346.
- [17] Y.K. Hnin, T.K. Tint, Production of fine aluminum powder from metallic aluminum, *The First International Conference on Interdisciplinary Research and Development*, 31 May–1 June, Thailand, 2011.
- [18] S.P. Mehrotra, Mathematical modeling of gas atomization process for metal powder production, *Powder Metall. Int.* 13 (2) (1981) 80–84.
- [19] A.N. Ghanim, Atomization of Aluminum by Unique Air Nozzle, *Journal of Babylon University/Pure and Applied Sciences* 19 (3) (2011) 1255–1263.
- [20] U. Backmark, N. Backstrom, L. Arenberg, Production of metal powder by ultrasonic gas atomization, *Powder Metall. Int.* 18 (15) (1986).
- [21] C.Y. Huang, S.R. Sheen, Synthesis of nanocrystalline and monodispersed copper particles of uniform spherical shape, *Mater. Lett.* 30 (1997) 357–361.
- [22] S.P. Wu, S.Y. Meng, Preparation of micron size copper powder with chemical reduction method, *Mater. Lett.* 60 (2006) 2438–2442.
- [23] S.N. Stanislav, B.M. Irina, Production of copper and copper alloy powders, *Handbook of Non-Ferrous Metal Powders* (2009) 331–368.
- [24] R.G. Blezard, The history of calcareous cements, *Lea's Chemistry of Cement and Concrete*, 4, 1998, pp. 1–23.
- [25] P. Alessi, A. Cortesi, I. Kikic, N.R. Foster, S.J. Macnaughton, I. Colombo, Particle production of steroid drugs using supercritical fluid processing, *Ind. Eng. Chem. Res.* 35 (12) (1996) 4718–4726.
- [26] W.M. Dean, L.F. John, C.P. Robert, D.S. Richard, Rapid expansion of supercritical fluid solutions: solute formation of powders, thin films, and fibers [J], *Ind. Eng. Chem. Res.* 26 (1987) 2298–2306.
- [27] A. Bertuccio, G. Vetter, *High pressure process technology, fundamentals and applications*, Industrial Chemistry Library, 9, Elsevier, Amsterdam, 2001.
- [28] L.X. Feng, J.P. Liang, D.C. Ge, Energy conservation for liquid CO₂ production from CO₂-rich exhaust gas, *Natural Gas Chemical Industry* 39 (2014) 62–64.